

Stainless Steels Types 321, 347 and 348 (UNS S32100, S34700 and S34800)

GENERAL PROPERTIES

Allegheny Ludlum Type 321 (S32100), 347 (S34700), and 348 (S34800) are stabilized stainless steels which offer as their main advantage an excellent resistance to intergranular corrosion following exposure to temperatures in the chromium carbide precipitation range from 800 to 1500°F (427 to 816°C). Type 321 is stabilized against chromium carbide formation by the addition of titanium. Types 347 and 348 are stabilized by the addition of columbium and tantalum. Type 348 has restricted cobalt and tantalum content for nuclear applications.

While Types 321, 347 and 348 continue to be employed for prolonged service in the 800 to 1500°F (427 to 816°C) temperature range, Type 304L has supplanted these stabilized grades for applications involving only welding or short time heating. (For information on Type 304L, consult the Allegheny Ludlum Blue Sheet on Types 302, 304, 304L and 305.)

Types 321, 347 and 348 stainless steels are also advantageous for high temperature service because of their good mechanical properties. Types 321, 347 and 348 stainless steels offer higher creep and stress rupture properties than Type 304 and, particularly, Type 304L which might also be considered for exposures where sensitization and intergranular corrosion are concerns. This results in higher elevated temperature allowable stresses for these stabilized alloys for ASME Boiler and Pressure Vessel Code applications. The Types 321, 347 and 348 alloys have maximum use temperatures of 1500°F (816°C) for code applications like Type 304, whereas T304L is limited to 800°F (426°C).

The properties of Type 348 are similar to the properties of Type 347, and according to ASTM A240 their chemical compositions are the same except for tantalum and cobalt contents. High carbon versions of all three alloys are available. These grades have UNS designations S32109, S34709, and S34809.

CHEMICAL COMPOSITION

Represented by ASTM A240 and ASME SA-240 specifications

Element	Weight Percent Maximum Unless Range is Specified		
	Type 321	Type 347	Type 348
Carbon*	0.08	0.08	0.08
Manganese	2.00	2.00	2.00
Phosphorus	0.045	0.045	0.045
Sulfur	0.030	0.030	0.030
Silicon	0.75	0.75	0.75
Chromium	17.00-19.00	17.00-19.00	17.00-19.00
Nickel	9.00-12.00	9.00-13.00	9.00-13.00
Columbium+	--	10xC min to	10xC min to
Tantalum**	--	1.00 max	1.00 max
Tantalum	--	--	0.10
Titanium**	5x(C+N) min to 0.70 max	--	--
Cobalt	--	--	0.20
Nitrogen	0.10	--	--
Iron	Balance	Balance	Balance

* Also H grade with Carbon 0.04 - 0.10%
** H grade minimum stabilizer is different formula

Referenced data are typical and should not be construed as maximum or minimum values for specification or for final design. Data on any particular piece of material may vary from those shown above.

RESISTANCE TO CORROSION

General Corrosion

Types 321, 347 and 348 alloys offer similar resistance to general, overall corrosion as the unstabilized chromium nickel Type 304. The Allegheny Ludlum Technical Data Blue Sheet on Type 304 may be consulted for an indication of resistance to corrosive media. Heating for long periods of time in the chromium carbide precipitation range may affect the general resistance of Types 321, 347 and 348 in severe corrosive media.

In most environments, all three alloys will show similar corrosion resistance; however, Type 321 in the annealed condition is somewhat less resistant to general corrosion in strongly oxidizing environments than annealed Type 347. For this reason, Type 347 is preferable for aqueous and other low temperature environments. Exposure in the 800 to 1500°F (427 to 816°C) temperature range lowers the overall corrosion resistance of Type 321 to a much greater extent than Type 347. Types 347 and 348 are used primarily in high temperature applications where high resistance to sensitization is essential, thereby preventing intergranular corrosion at lower temperatures.

Intergranular Corrosion

Allegheny Ludlum Stainless Types 321, 347 and 348 have been developed for applications where the unstabilized chromium-nickel steels, such as Type 304, would be susceptible to intergranular corrosion.

When the unstabilized chromium-nickel steels are held in or slowly cooled through the range of 800 to 1500°F (427 to 816°C), chromium carbide is precipitated at the grain boundaries. In the presence of certain strongly corrosive media, these grain boundaries are preferentially attacked, a general weakening of the metal results, and a complete disintegration may occur.

Organic media or weakly corrosive aqueous agents, milk and other dairy products, or atmospheric conditions rarely produce intergranular corrosion even when large amounts of precipitated carbides are present. When thin gage material is welded the time in the temperature range of 800 to 1500°F (427 to 816°C) is so short that with most corroding media the unstabilized

types are generally satisfactory. The extent to which carbide precipitation may be harmful depends upon the length of time the alloy was exposed to 800 to 1500°F (427 to 816°C) and upon the corrosive environment. Even the longer heating times involved in welding heavy gages are not harmful to the unstabilized "L" grade alloys where the carbon content is kept to low amounts of 0.03% or less.

The high resistance of the stabilized Type 321, Type 347 and Type 348 stainless steels to sensitization and intergranular corrosion is illustrated by data for the Type 321 alloy in the Copper-Copper Sulfate -16% Sulfuric Acid Test (ASTM A262, Practice E) below. Mill annealed samples were given a sensitizing heat treatment consisting of soaking at 1050°F (566°C) for 48 hours prior to the test.

Intergranular Corrosion Test Long-Term Sensitization* Results ASTM A262 Practice E			
Alloy	Rate (ipm)	Bend	Rate (mpy)
304	0.81	dissolved	9720.0
304L	0.0013	IGA	15.6
321	0.0008	IGA	9.6
347	0.0005	NO IGA	6.0

*Annealed 1100°F, 240 hours

The absence of intergranular attack (IGA) in the Type 347 specimens shows that they did not sensitize during this thermal exposure. The low corrosion rate exhibited by the Type 321 specimens shows that even though it suffered some IGA, it was more resistant than Type 304L under these conditions. All of these alloys are far superior to regular Type 304 stainless steel under the conditions of this test.

In general, Types 321, 347 and 348 are used for heavy welded equipment which cannot be annealed and for equipment which is operated between 800 to 1500°F (427 to 816°C) or slowly cooled through this range. Experience gained in a wide range of service conditions has provided sufficient data to generally predict the possibility of intergranular attack in most applications.

Referenced data are typical and should not be construed as maximum or minimum values for specification or for final design. Data on any particular piece of material may vary from those shown above.

Please also review our comments under the HEAT TREATMENT section.

STRESS CORROSION CRACKING

The Type 321, 347 and 348 austenitic stainless steels are susceptible to stress corrosion cracking (SCC) in halides similar to Type 304 stainless steel. This results because of their similarity in nickel content. Conditions which cause SCC are: (1) presence of halide ion (generally chloride), (2) residual tensile stresses, and (3) environmental temperatures in excess of about 120°F (49°C). Stresses may result from cold deformation during forming operations, or from thermal cycles encountered during welding operations. Stress levels may be reduced by annealing or stress-relieving heat treatments following cold deformation. The stabilized

are common. The stabilized Types 321, 347 and 348 alloys offer a solution to polythionic acids SCC by resisting sensitization during elevated temperature service. For optimum resistance, these alloys should be used in the thermally stabilized condition if service-related conditions may result in sensitization.

Pitting/Crevice Corrosion

The resistance of the stabilized Types 321, 347 and 348 alloys to pitting and crevice corrosion in the presence of chloride ion is similar to that of Type 304 or 304L stainless steels because of similar chromium content. Generally, 100 ppm chloride in aqueous environments is considered to be the limit for both the unstabilized and

Halide (Chloride) Stress Corrosion Tests, Type 321		
Test	U-Bend (Highly Stressed) Samples	
42% Magnesium Chloride, Boiling	Base Metal	Cracked, 24-71 hours
	Welded	Cracked 24-71 hours
33% Lithium Chloride, Boiling	Base Metal	Cracked Within 18 hours
	Welded	Cracked Within 18 hours
26% Sodium Chloride, Boiling	Base Metal	No Cracks 1000 hours Cracked Within 475 hours
	Welded	Cracked Within 525-621 hours

Types 321, 347 and 348 alloys are good choices for service in the stress relieved condition in environments which might otherwise cause intergranular corrosion for unstabilized alloys.

The Types 321, 347 and 348 alloys are particularly useful under conditions which cause polythionic acid stress corrosion of non-stabilized austenitic stainless steels, such as Type 304. Exposure of non-stabilized austenitic stainless steel to temperatures in the sensitizing range will cause the precipitation of chromium carbides at grain boundaries. On cooling to room temperature in a sulfide-containing environment, the sulfide (often hydrogen sulfide) reacts with moisture and oxygen to form polythionic acids which attack the sensitized grain boundaries. Under conditions of stress, intergranular cracks form. Polythionic acid SCC has occurred in oil refinery environments where sulfides


the stabilized alloys, particularly if crevices are present. Higher levels of chloride ion might cause crevice corrosion and pitting. For more severe conditions of higher chloride level, lower pH and/or higher temperature, alloys with molybdenum, such as Type 316 or AL-6XN® alloy, should be considered. The stabilized Types 321, 347 and 348 alloys pass the 100 hour, 5 percent neutral salt spray test (ASTM B117) with no rusting or staining of samples. However, exposure of these alloys to salt mists from the ocean would be expected to cause pitting and crevice corrosion accompanied by severe discoloration. The Types 321, 347 and 348 alloys are not recommended for exposure to marine environments.

Referenced data are typical and should not be construed as maximum or minimum values for specification or for final design. Data on any particular piece of material may vary from those shown above.

The reader is invited to contact the Allegheny Ludlum Technical Center with questions concerning the suitability of the stabilized alloys for specific environments.

ELEVATED TEMPERATURE OXIDATION RESISTANCE

Types 321, 347, and 348 exhibit oxidation resistance comparable to the other 18–8 austenitic stainless steels. Oxidation test data for Type 347 is presented graphically and in tabular form. Specimens prepared from standard mill-finish production material were exposed in ambient laboratory air at elevated temperatures. Periodically, specimens were removed from the high temperature environment and weighed to determine the extent of scale formation. Test results are reported as a weight change in units of milligrams per square centimeter and reflect the average from a minimum of two different test specimens.

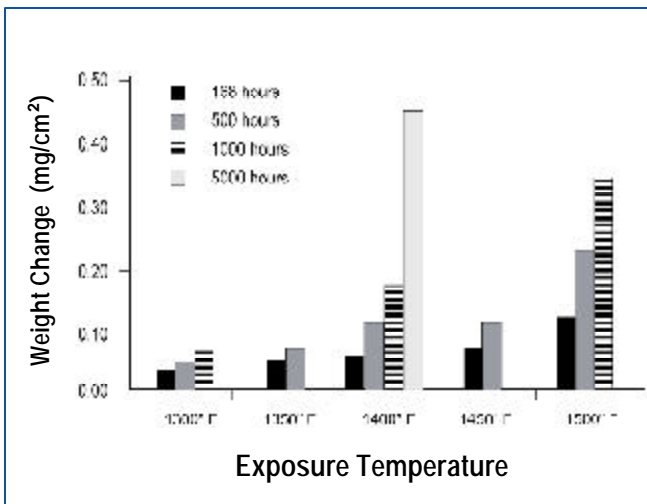

Weight Change (mg/cm ²)					
Exposure Time	1300°F	1350°F	1400°F	1450°F	1500°F
168 hours	0.032	0.046	0.054	0.067	0.118
500 hours	0.045	0.065	0.108	0.108	0.221
1,000 hours	0.067	--	0.166	--	0.338
5,000 hours	--	--	0.443	--	--

Types 321, 347, and 348 differ primarily by small alloying additions unrelated to factors affecting the oxidation resistance. Therefore, these results should be representative of all three grades. However, since the rate of oxidation can be influenced by the exposure environment and factors intrinsic to specific product forms, these results should be interpreted only as a general indication of the oxidation resistance of these grades. Allegheny Ludlum's Technical Center can supply data and prior experience pertaining to specific applications on request.

PHYSICAL PROPERTIES

The physical properties of Types 321, 347 and 348 are quite similar and, for all practical purposes, may be considered to be the same. The values given in the table on this page may be used to apply to all three steels.

When properly annealed, the Types 321, 347 and 348 stainless steels consist principally of austenite and carbides of titanium or columbium. Small amounts of ferrite may or may not be present in the microstructure. Small amounts of sigma phase may form during long time exposure in the 1000 to 1500°F (593 to 816°C) temperature range.

The stabilized Types 321, 347 and 348 stainless steels are not hardenable by heat treatment.

The overall heat transfer coefficient of metals is determined by factors in addition to thermal conductivity of the metal. In most cases, film coefficients, scaling, and surface conditions are such that not more than 10 to 15 percent more surface area is required for stainless steels than for other metals having higher thermal conductivity. The ability of stainless steels to maintain clean surfaces often allow better heat transfer than other metals having higher thermal conductivity.

Magnetic Permeability

The stabilized Types 321, 347 and 348 alloys are generally non-magnetic in the annealed condition with magnetic permeability values typically less than 1.02 at 200H. Permeability values may vary with composition and will increase with cold work. Permeability of welds containing ferrite will be higher.

Referenced data are typical and should not be construed as maximum or minimum values for specification or for final design. Data on any particular piece of material may vary from those shown above.

Technical Data BLUE SHEET

Typical Physical Properties			
Density			
Grade		g/cm ³	lb/in ³
321		7.92	0.286
347		7.96	0.288
348		7.96	0.289
Modulus of Elasticity in Tension			
28 x 10 ⁶ psi 193 GPa			
Mean Coefficient of Linear Thermal Expansion			
Temperature Range °C °F		cm/cm °C	in/in °F
20 - 100	68 - 212	16.6 x 10 ⁻⁶	9.2 x 10 ⁻⁶
20 - 600	68 - 1112	18.9 x 10 ⁻⁶	10.5 x 10 ⁻⁶
20-1000	68 - 1832	20.5 x 10 ⁻⁶	11.4 x 10 ⁻⁶
Thermal Conductivity			
Temperature Range °C °F		W/m•K	Btu•in/hr•ft ² • °F
20-100	68-212	16.3	112.5
20-500	68-932	21.4	147.7
Specific Heat			
Temperature Range °C °F		J/kg K	Btu/lb•°F
0-100	32-212	500	0.12
Electrical Resistivity			
Temperature Range °C °F		microhm•cm	
20	68	72	
100	213	78	
200	392	86	
400	752	100	
600	1112	111	
800	1472	121	
900	1652	126	
Melting Range			
°C		°F	
1398-1446		2550-2635	

MECHANICAL PROPERTIES

Room Temperature Tensile Properties

Minimum mechanical properties of the stabilized Types 321, 347 and 348 chromium-nickel grades in the annealed condition (2000°F [1093°C], air cooled) are shown in the table on the next page. The test samples were prepared from sheet material.

Elevated Temperature Tensile Properties

Typical elevated temperature mechanical properties for Types 321, 347 and 348 sheet/strip are shown below. Strength of these stabilized alloys is distinctly higher than that of non-stabilized Type 304 alloy at temperatures of 1000°F (538°C) and above.

High carbon Types 321H, 347H and 348H (UNS S32109, S34709 and S34809, respectively) have higher strength at temperatures above 1000°F (537°C). ASME maximum allowable design stress data for Type 347H reflects the higher strength of this grade in comparison to the lower carbon Type 347 grade. The Type 321H and Type 348H grades are not permitted for Section VIII applications and are limited to 800°F (427°C) use temperatures for Section III code applications.

Creep and Stress Rupture Properties

Typical creep and stress rupture data for Types 321, 347 and 348 stainless steels are shown in the figures below. The elevated temperature creep and stress rupture strengths of the stabilized steels are higher than those of unstabilized Type 304 and 304L. These superior properties for the Types 321, 347 and 348 alloys permit design of pressure containing components for elevated temperature service to higher stress levels

Impact Strength Types 321, 347, & 348			
Test Temperature		Charpy Impact Energy Absorbed	
°F	°C	Ft-lbs	Joules
75	24	90	122
-25	-32	66	89
-80	-62	57	78

Referenced data are typical and should not be construed as maximum or minimum values for specification or for final design. Data on any particular piece of material may vary from those shown above.

Minimum Room Temperature Mechanical Properties Per ASTM A 240 and ASME SA-240						
Type	Yield Strength .2% Offset psi (MPa)	Ultimate Tensile Strength psi (MPa)	Elongation in 2 in. (%)	Hardness, Maximum		
				Plate	Sheet	Strip
321	30,000 (205)	75,000 (515)	40.0	217 Brinell	95 Rb	95 Rb
347	30,000 (205)	75,000 (515)	40.0	201 Brinell	92 Rb	92 Rb
348	30,000 (205)	75,000 (515)	40.0	201 Brinell	92 Rb	92 Rb

Typical Elevated Temperature Tensile Properties Type 321 (0.036 inch thick / 0.9 mm thick)				
Test Temperature		Yield Strength .2% Offset psi (MPa)	Ultimate Tensile Strength psi (MPa)	% Elongation in 2 in.
°F	°C			
68	20	31,400 (215)	85,000 (590)	55.0
400	204	23,500 (160)	66,600 (455)	38.0
800	427	19,380 (130)	66,300 (455)	32.0
1000	538	19,010 (130)	64,400 (440)	32.0
1200	649	19,000 (130)	55,800 (380)	28.0
1350	732	18,890 (130)	41,500 (285)	26.0
1500	816	17,200 (115)	26,000 (180)	45.0

Typical Elevated Temperature Tensile Properties Type 347 and Type 348 (0.060 inch thick / 1.54 mm thick)				
Test Temperature		Yield Strength .2% Offset psi (MPa)	Ultimate Tensile Strength psi (MPa)	% Elongation in 2 in.
°F	°C			
68	20	36,500 (250)	93,250 (640)	45.0
400	204	36,600 (250)	73,570 (505)	36.0
800	427	29,680 (205)	69,500 (475)	30.0
1000	538	27,400 (190)	63,510 (435)	27.0
1200	649	24,475 (165)	52,300 (360)	26.0
1350	732	22,800 (155)	39,280 (270)	40.0
1500	816	18,600 (125)	26,400 (180)	50.0

as recognized in the ASME Boiler and Pressure Vessel Code.

testing temperatures. Data for Type 321 would be expected to be similar.

Impact Strength

Types 321 and 347 have excellent toughness at room and sub-zero temperatures. In the following table are Charpy V-notch impact values for annealed Type 347 after holding the samples for 1 hour at the indicated


Fatigue Strength

The fatigue strength of practically every metal is affected by corrosive conditions, surface finish, form, and mean stress. For this reason, no definite values can be shown which would be representative of the fatigue strength under all operating conditions. The fatigue endurance limits of Types 321 and 347 are approximately 35% of their tensile strengths.


Referenced data are typical and should not be construed as maximum or minimum values for specification or for final design. Data on any particular piece of material may vary from those shown above.

Technical Data BLUE SHEET


**CREEP STRENGTH
ANNEALED TYPE 321**

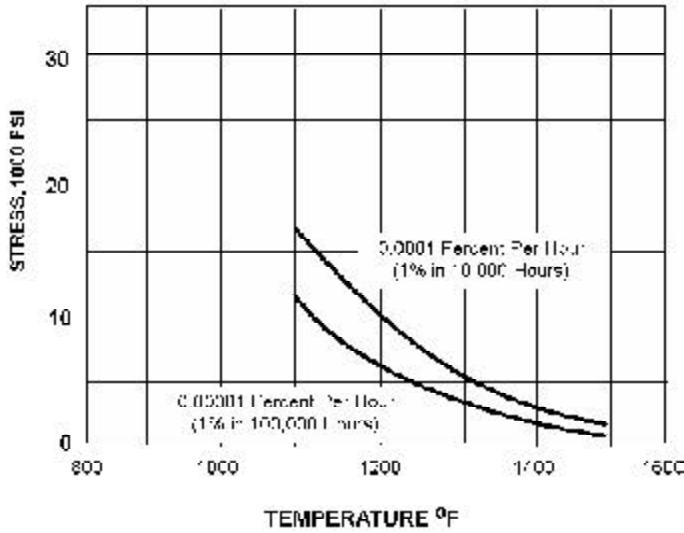


**CREEP STRENGTH
ANNEALED TYPES 347 and 348**

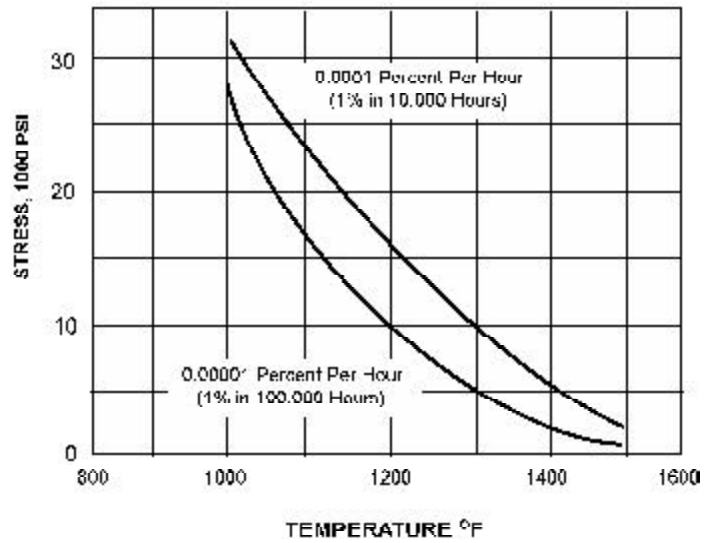

**STRESS RUPTURE STRENGTH
ANNEALED TYPE 301**

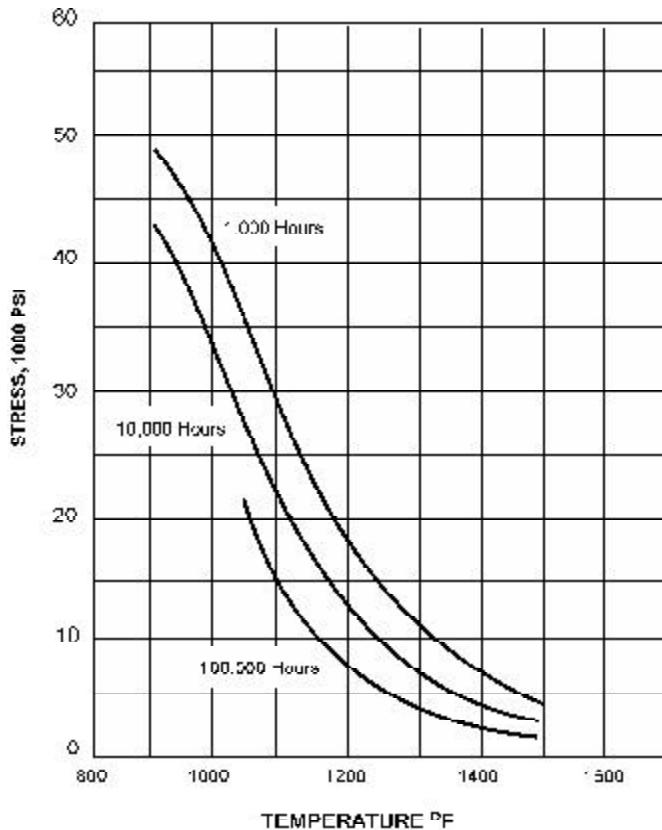

**STRESS RUPTURE STRENGTH
ANNEALED TYPE 347 and 348**

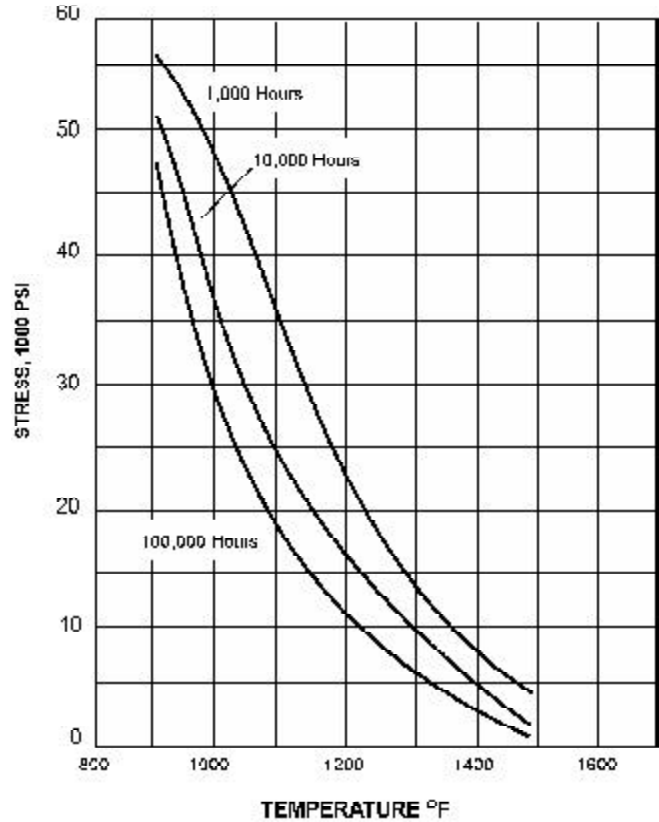

Referenced data are typical and should not be construed as maximum or minimum values for specification or for final design. Data on any particular piece of material may vary from those shown above.

FABRICATION

Welding

Austenitic stainless steels are considered to be the most weldable of the high-alloy steels and can be welded by all fusion and resistance welding processes.

Two important considerations in producing weld joints in the austenitic stainless steels are: 1) preservation of corrosion resistance and 2) avoidance of cracking.

It is important to maintain the level of stabilizing element present in Types 321, 347 and 348 during welding. Type 321 is more prone to loss of titanium. Types 347 and 348 are more resistant to loss of columbium. Care needs to be exercised to avoid pickup of carbon from oils and other sources and nitrogen from air. Weld practices which include attention to cleanliness and good inert gas shielding are recommended for these stabilized grades as well as other non-stabilized austenitic alloys.

Weld metal with a fully austenitic structure is more susceptible to cracking during the welding operation. For this reason, Types 321, 347 and 348 alloys are designed to resolidify with a small amount of ferrite to minimize cracking susceptibility. Columbium stabilized stainless steels are more prone to hot cracking than titanium stabilized stainless steels.

Matching filler metals are available for welding Types 321 and 347 stabilized stainless steels. The Type 347 filler metal is sometimes used to weld the Type 321 alloy as well as the Type 348 alloy.

These stabilized alloys may be joined to other stainless steels or carbon steel. Type 309 (23% Cr-13.5% Ni) or nickel-base filler metals have been used for this purpose.

HEAT TREATMENT

The annealing temperature range for Types 321 and 347 is 1800 to 2000°F (928 to 1093°C). While the primary purpose of annealing is to obtain softness and high ductility, these steels may also be stress relief an-

nealed within the carbide precipitation range 800 to 1500°F (427 to 816°C), without any danger of subsequent intergranular corrosion. Relieving strains by annealing for only a few hours in the 800 to 1500°F (427 to 816°C) range will not cause any noticeable lowering in the general corrosion resistance, although prolonged heating within this range does tend to lower the general corrosion resistance to some extent. As emphasized, however, annealing in the 800 to 1500°F (427 to 816°C) temperature range does not result in a susceptibility to intergranular attack.

For maximum ductility, the higher annealing range of 1800 to 2000°F (928 to 1093°C) is recommended.

When fabricating chromium-nickel stainless steel into equipment requiring the maximum protection against carbide precipitation obtainable through use of a stabilized grade, it is essential to recognize that there is a difference between the stabilizing ability of columbium and titanium. For these reasons the degree of stabilization and of resulting protection may be less pronounced when Type 321 is employed.

When maximum corrosion resistance is called for, it may be necessary with Type 321 to employ a corrective remedy which is known as a stabilizing anneal. It consists of heating to 1550 to 1650°F (843 to 899°C) for up to 5 hours depending on thickness. This range is above that within which chromium carbides are formed and is sufficiently high to cause dissociation and solution of any that may have been previously developed. Furthermore, it is the temperature at which titanium combines with carbon to form harmless titanium carbides. The result is that chromium is restored to solid solution and carbon is forced into combination with titanium as harmless carbides.

This additional treatment is required less often for the columbium-stabilized Type 347 and 348 grades.

When heat treatments are done in an oxidizing atmosphere the oxide should be removed after annealing in a descaling solution such as a mixture of nitric and hydrofluoric acids. These acids should be thoroughly rinsed off the surface after cleaning.

These alloys cannot be hardened by heat treatment.

Cleaning

Despite their corrosion resistance, stainless steels need care in fabrication and during use to maintain their surface appearance even under normal conditions of service.

In welding, inert gas processes are used. Scale or slag that forms from welding processes is removed with a stainless steel wire brush. Carbon steel wire brushes will leave carbon steel particles in the surface which will eventually produce surface rusting. For more severe applications, welded areas should be treated with a descaling solution such as a mixture of nitric and hydrofluoric acids to remove the heat tint, and these acids should be subsequently washed off.

For material exposed to inland, light industrial or milder service, minimum maintenance is required. Only sheltered areas need occasional washing with a stream of pressurized water. In heavy industrial areas, frequent washing is advisable to remove dirt deposits which might eventually cause corrosion and impair the surface appearance of the stainless steel.

Design can aid cleanability. Equipment with rounded corners, fillets and absence of crevices facilitates cleaning as do smooth ground welds and polished surfaces.

SURFACE FINISHES

A range of surface finishes is available. These are designated by a series of numbers.

Number 1 Finish – is hot rolled, annealed and descaled. It is available for plate and sheet and is used for functional applications where a smooth decorative finish is not important.

Number 2D Finish – is a dull finish produced by cold rolling, annealing and descaling. This finish is favorable for the retention of lubricants in drawing or other forming operations and is preferred for deep drawn and formed parts.

Number 2B Finish – is a brighter finish than 2D. It is produced much like the 2D finish except that the final cold rolling is done with smooth polished rolls. This is a general-purpose finish used for all but severe cold forming. Because it is smoother as produced, it is more readily polished than 1 or 2D finishes.

Number 2BA Finish – is a very smooth finish produced by cold rolling and bright annealing. A light pass using highly polished rolls produces a glossy finish. A 2BA finish may be used for lightly formed application where a glossy finish is desired in the as-formed part.

Polished Finishes – a variety of ground and polished finishes is available on request. Because special equipment or processes are used to develop these finishes, not all finishes are available in the range of products produced by Allegheny Ludlum. Surface finish requirements should be discussed with Allegheny Ludlum mill representatives.

AVAILABILITY AND SPECIFICATIONS

Types 321, 347 and 348 stainless steels are available from Allegheny Ludlum as plate, sheet and strip. These products are sold primarily in the mill-annealed condition. Some temper rolled strip products can be supplied. These are handled on an inquiry basis.

Product Form	Specifications, Types 321, 347 & 348		
	ASTM	ASME	AMS
Plate, Sheet and Strip	A 240/ A 240M	SA-240/SA-240M	5510 [1] 5512 [2]

[1] Type 321 only

[2] Type 347 only

In Section II, Part D of the ASME Boiler and Pressure Vessel Code, Types 321, 347 and 348 stainless steels are assigned allowable stresses for a variety of product forms to a maximum use temperature of 1500°F (816°C).

Referenced data are typical and should not be construed as maximum or minimum values for specification or for final design. Data on any particular piece of material may vary from those shown above.

